

## STUDY CHARACTERIZATION OF $Co_{0.3}Zn_{0.7}Fe_2O_4$ NANOPARTICLES BY CO-PRECIPIATION METHOD WITHIN TWO TECHNIQUES

Ahmed Saied Faheim El-Saay<sup>1\*</sup>, Abd El Fattah Mustafa Khourshid<sup>2</sup>

Wagih W. Marzouk<sup>3</sup>, Samir Mohamed Abdel-Rahman<sup>4</sup>

<sup>1</sup>Mechanical & electrical research institute, National water research Centre, Egypt

<sup>2</sup>Material Engineering Department, Faculty of Engineering, Tanta University, Egypt

<sup>3</sup>Production & Design Department, Faculty of Engineering, Minia University, Egypt

<sup>4</sup>Mechanical & electrical research institute, National water research Centre, Egypt

---

**ABSTRACT:** *The  $Co_{0.3}Zn_{0.7}Fe_2O_4$  nanocrystalline synthesized by the Co-precipitation method with two techniques based on different in initial molar concentration (pH suspension). The structural and magnetic properties of the products were determined and characterized in detail by X-ray diffraction (XRD), High Resolution -Transmission Electron Microscope (HR-TEM), Fourier Transform Infrared (FTIR) and vibrating sample magnetometer (VSM). The results suggest the grain size for first technique in the range of 6.14 : 13 nm and second technique in the range of 8.8: 24.4 nm as the calcination temperature increases from 100 to 600°C respectively with different in initial molar concentration (pH suspension) for all techniques. X-ray analysis showed that the samples were cubic spinel structural (kind of inverse spinel oxide). The crystallinity is improved with the increases calcination temperature for all techniques and that proved by the FT-IR & XRD results and compound purity fabricated. HR-TEM analysis showed that nanoparticles size and the shape based on the initial molar concentration (pH suspension) & the calcination temperatures and also indicates that degree of agglomeration for all samples. VSM analysis showed that all the coercivity values were low enough to emphasize that the ferrite was a soft ferrite or super-paramagnetic behavior for most samples.*

**KEYWORDS:** Calcination Process, Co-precipitation method;  $Co_{0.3}Zn_{0.7}Fe_2O_4$  Magnetic Properties, Anoparticles, Ferrite,.

---

## INTRODUCTION

Ferrite types with chemical composition variance and the spinal crystal structure are magnetic ceramics (such as Co ferrite, Zn ferrite and Co Zn ferrite) of great importance in the manufacturing of insulators and electronic industrials. The physical, chemical and magnetic properties of ferrite are depends on various parameters such as processing conditions, calcination temperature and time as well as on their chemical composition [1, 2]. The properties of these materials mainly depend on their shape, size, and structure, which are strongly determined by the fabrication processes [3,4].

There are several different fabrication techniques used to produce ferrites such as sol-gel, combustion methods, hydrothermal, mechano-chemical and refluxing, However most of them cannot be economically applied on a large scale because they required high vacuum system, complicated experimental steps and high reaction temperatures, but co-precipitation method is considered to be economical technique for ferrite production [5,6,7,8,9,10,11,12,13].

The aim of the present work is to the synthesis of  $\text{Co}_{0.3}\text{Zn}_{0.7}\text{Fe}_2\text{O}_4$  Nanoparticles are prepared by Co-precipitation method with two techniques for its manufactured. The structural and magnetic properties of nano-crystalline cobalt zinc ferrite can be controlled by adjusting the synthesis route in the initial mixtures. The synthesized nano- crystals have been characterized by XRD, HR-TEM, EDX, vibrating sample magnetometer (VSM) and FT-IR, provided below are the investigation details.

## EXPERIMENTAL

### Materials

All chemical re-agents—ferric chloride  $\text{FeCl}_3$ , cobalt(II) chloride  $\text{CoCl}_2$ , zinc(II) chloride  $\text{ZnCl}_2$  and sodium hydroxide  $\text{NaOH}$ —were purchased from (El-Gomhouria Co. for Drugs), Egypt and used as received without further treatment.

### Instrumentation



X-ray powder diffraction analysis was conducted on a Bruker Axs-D8 Advace Diffractometer (XRD). FTIR transmission spectra were taken on Perkin Elmer Spectrum BX model Infrared Spectrophotometer from 2000 to  $400\text{ cm}^{-1}$ . High Resolution- Transmission Electron Microscopy (HR-TEM) analysis was performed on (JEOL 2000FX). Magnetic measurements were carried out with the Quantum Design Model 6000 Vibrating Sample Magnetometer (VSM) and parameters like specific saturation magnetization ( $M_s$ ), coercive force ( $H_c$ ) and remanence ( $M_r$ ) were evaluated.

### Procedures


The  $\text{Co}_{0.3}\text{Zn}_{0.7}\text{Fe}_2\text{O}_4$  Nanoparticles are prepared by Co-precipitation method with two techniques, So that the Co-precipitation method depends on parameters such as reaction temperature, pH of the suspension, initial molar concentration etc. [14].

In the first and second techniques the mixed solution of  $\text{CoCl}_2$ ,  $\text{ZnCl}_2$  and  $\text{FeCl}_3$  in their respective stoichiometry (100 ml of 0.3 M  $\text{CoCl}_2$ , 100 ml of 0.7 M  $\text{ZnCl}_2$  and 100 ml of 2 M  $\text{FeCl}_3$ ) was prepared and kept at  $60^\circ\text{C}$ . And the preparation of  $\text{NaOH}$  solution (1 M dissolved in 1200 ml of distilled water), but the difference between two techniques are in first using two burettes for the mix of solution of  $\text{CoCl}_2$ ,  $\text{ZnCl}_2$  and  $\text{FeCl}_3$ , and the second burette for  $\text{NaOH}$  solution in the same time put drops from two burettes in the beaker contains one liter of water within 10 s under constant stirring until pH become 12 as shown in table (1) in Figure (a), but in second technique mix of solution of  $\text{CoCl}_2$ ,  $\text{ZnCl}_2$  and  $\text{FeCl}_3$  put them in beaker the boiling solution of  $\text{NaOH}$  was added to the mix of solutions within 10 s under constant stirring until pH become 12 as shown in table (1) in Figure (b).

Nano Co Zn ferrites are fabricated by transformation of metal salts into hydroxides. The transformation process occurs immediately, followed by transformation of hydroxides into ferrites. At first solid hydroxides of metals in the form of fine particles were obtained by the co-precipitation of metal cations in alkaline medium (co-precipitation step):

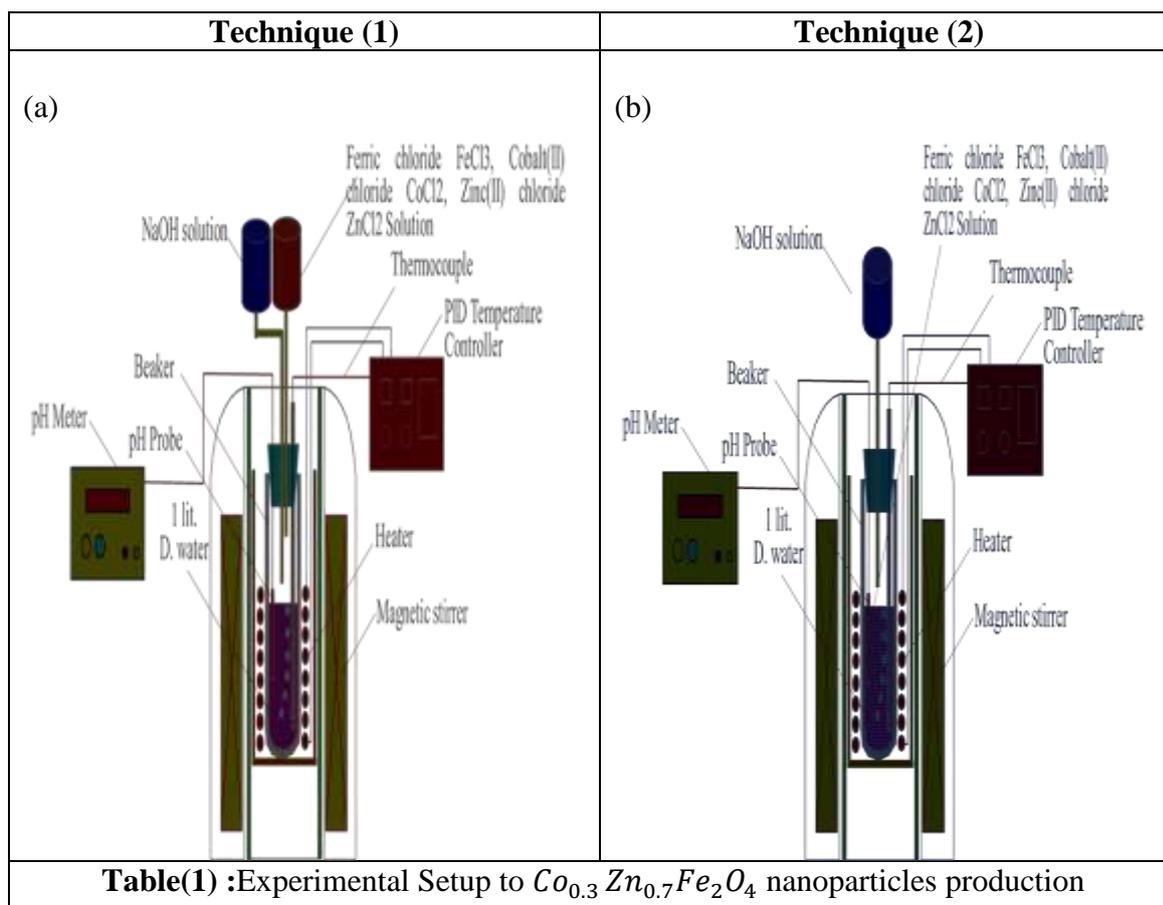

The complex zinc substituted ferrites are obtained by subjecting the solid solution of metal hydroxides to heating in the alkaline medium:




The solutions been preserved at 80 °C for 2 h. to transform of hydroxides into spinel ferrite [2, 14]. Enough amount of Nanoparticles were collected at this stage by using filtration process under vacuum pressure for samples separation and washing samples several times with distilled water and dried at 100°C temperature and samples subjected for calcination process at 600 °C.

## RESULTS AND DISCUSSIONS


### Physical characterization (XRD analysis)

In figures (1:4) show the X-ray diffraction patterns of  $Co_{0.3}Zn_{0.7}Fe_2O_4$  nanoparticles samples at 100°C and 600°C. The diffraction patterns show six reflection planes (220), (311), (400), (422), (511), (440) [15]. These clear-cut musings without any confusion, exhibits the formation of a spinel cubic structure and the (hkl) value of the entire peak are which refer to face centered cubic (F.C.C.) structure ( kind of inverse spinel oxide). The broad x-ray diffraction peak for the samples for two techniques at 600°C suggest that the ferrite particles

are of nano size, whereas calcination achieve about increase in grain size which leads rise to sharp clear-cut peaks.

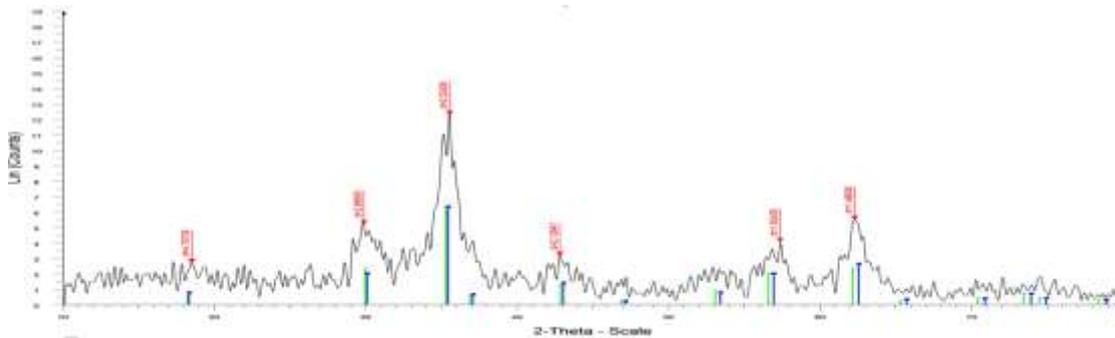


**Fig (1):** XRD pattern for of  $\text{Co}_{0.3}\text{Zn}_{0.7}\text{Fe}_2\text{O}_4$  nanoparticles for 1<sup>st</sup> technique at 100°C

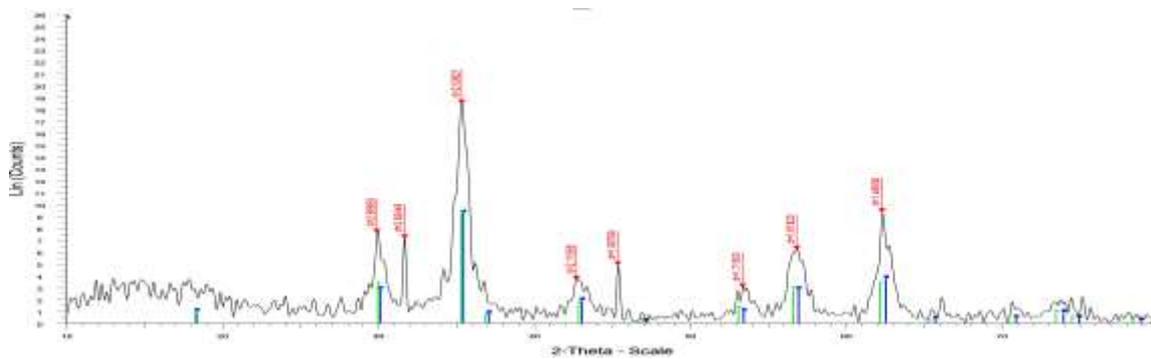


**(2):** XRD pattern for of  $\text{Co}_{0.3}\text{Zn}_{0.7}\text{Fe}_2\text{O}_4$  nanoparticles for 1<sup>st</sup> technique at 600°C

**Fig**

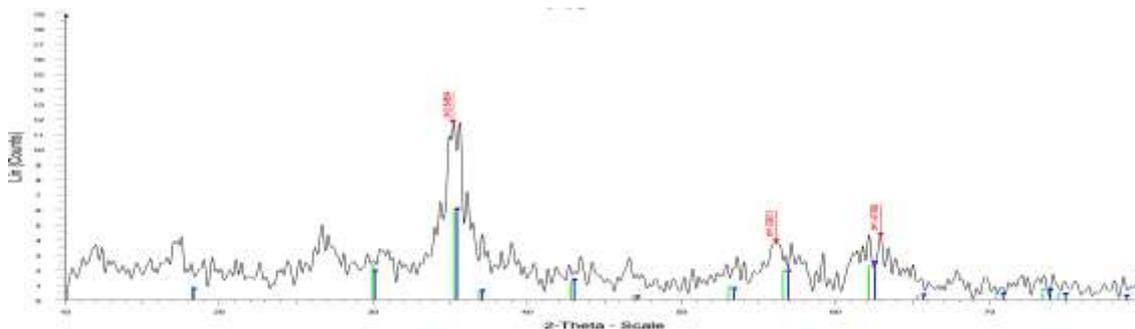

**(3):** XRD pattern for of  $\text{Co}_{0.3}\text{Zn}_{0.7}\text{Fe}_2\text{O}_4$  nanoparticles for 2<sup>nd</sup> technique at 100°C

**Fig**

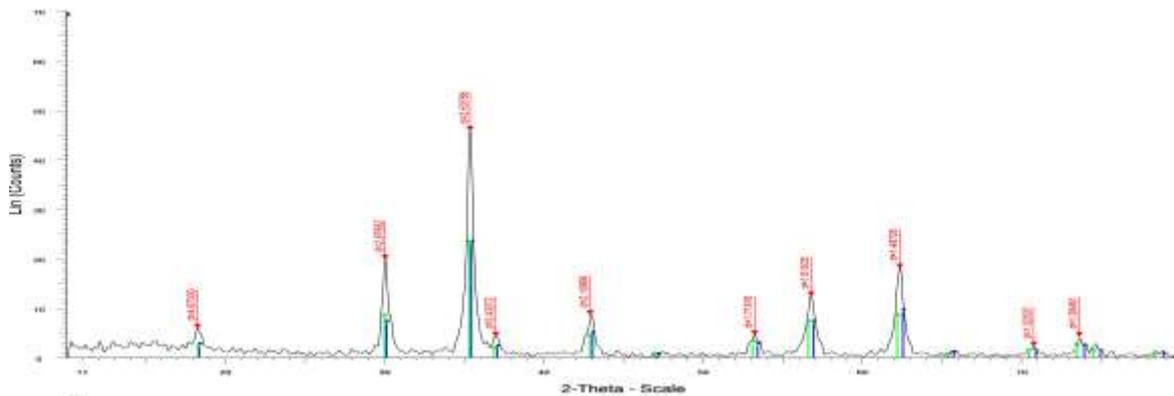

**Fig (4):** XRD pattern for of  $\text{Co}_{0.3}\text{Zn}_{0.7}\text{Fe}_2\text{O}_4$  nanoparticles for 2<sup>nd</sup> technique at 600°C


The XRD analysis, the average grain size for each samples has been calculated from the XRD line width of the highest intensity peak (311) using Debye Scherrer equation [16], whereas the grain size for first technique in the range of 6.14 : 13 nm but second technique in the range of 8.8: 24.4 nm. In all cases, the grain size decreases with initial molar concentration increased (pH suspension), whereas grain size increases with the increase of calcination temperature. The reduction in grain size can be explained by the particle size effect, more specifically, the effect of surface stress [17].

The initial molar concentration (pH suspension) & calcination parameter with different techniques for sample preparation brought about different changes in the structural properties such as degree of crystallinity, lattice constant, unit cell volume, ionic radii, the distance between the magnetic ions and bond lengths on tetrahedral sites and octahedral sites of cubic spinel structure for each samples [18]. The lattice constant ( $a_0$ ) can be calculated by Nelson - Riley function and using a least square fit method, whereas the lattice constant for first technique in the range of 8.38: 8.51nm but second technique in the range of 8.42: 8.53 nm.

#### **Transmission Electron Microscope (TEM) measurement and Analysis:**

The Nano-Structure of the  $\text{Co}_{0.3}\text{Zn}_{0.7}\text{Fe}_2\text{O}_4$  nanoparticles praperated by Co-precipitation method with change in initial molar concentration (pH suspension) & calcination parameter (at 100 °C and 600 °C), are investigated by HRTEM.

The table (2) shows the  $\text{Co}_{0.3}\text{Zn}_{0.7}\text{Fe}_2\text{O}_4$  nanoparticles fabrication by two techniques. The first technique Fig.(a, b) show spherical with uniform size with the calcination temperature increased ,but second technique Fig.(c) show spherical with uniform size at 100°C, but the calcination temperature increase for same sample at 600°C occurred change in shapes (spherical and rods form ) with different size for particles as show in Fig.(d) .

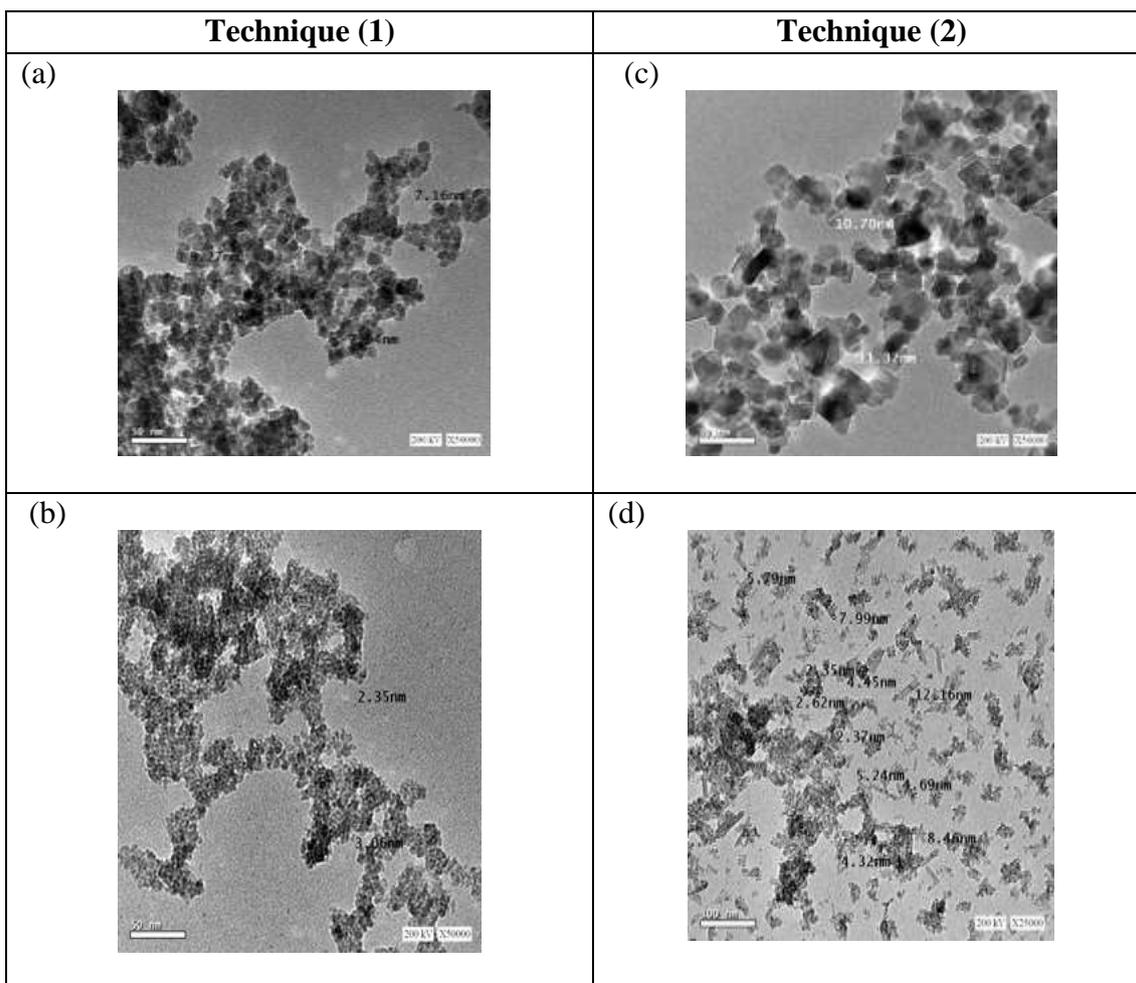


**Table (2):** TEM images

Therefore, the HR-TEM results proved the XRD results that appear the nanoparticle size is dependent on the initial molar concentration (pH suspension) and calcination temperature. It is shown that the particles in first technique has a high degree of agglomeration but second technique has a low degree of agglomeration caused by mutual interaction between particles which arises from some parameters such as Vander-walls forces, capillary forces and electrostatic forces. Adding hydroxide solution directly leads to complete the nucleation and growth in a few seconds that effects on agglomeration of particles.

### FT-IR analysis

Pradeep and Chandrasekaran are proposed M-O stretching band in ferrites with the frequency bands near  $564\text{-}588\text{ cm}^{-1}$  and  $425\text{-}442\text{ cm}^{-1}$  which refer to the tetrahedral and octahedral clusters in ferrites form, therefore in table (3) show FT-IR analysis are confirms the presence of ferrites phase[19].

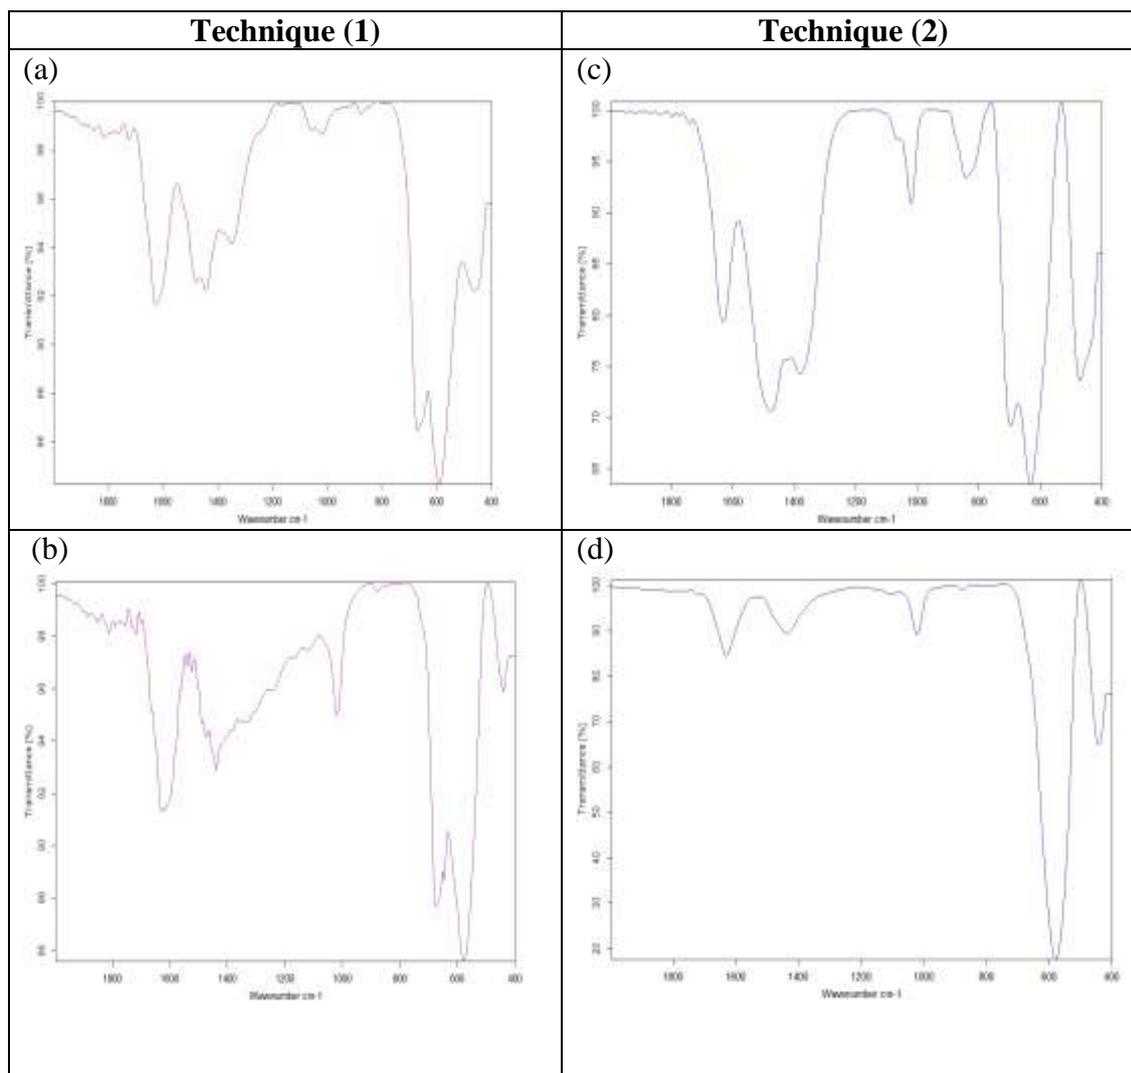


**Table (3):** The FTIR absorption bands for two techniques

The cations distribution analysis for crystal structure in FT-IR spectra are dependent on the vibrational mode of tetrahedral and octahedral clusters but tetrahedral clusters is higher as compared to that of octahedral clusters, which is attributed to the shorter bond length of tetrahedral clusters.

Therefore, FT-IR analysis tool to assess the purity of a compound, from Table (3) show the FTIR absorption bands for two techniques at room temperature in the wave number range of  $400\text{--}2000\text{ cm}^{-1}$ . It is clear that the higher frequency band is (U1) around  $600\text{ cm}^{-1}$  and the lower frequency band (U2) is around  $400\text{ cm}^{-1}$  shows that in table (3), but in Fig(d) the sample for second technique at  $600^\circ\text{C}$  has high purity and degree of crystallinity which confirms the presence spinal crystal structure. Therefore, the FT-IR results proved the XRD results that appear the cations distribution, crystal structure phase and degree of crystallinity. The highest one corresponds to the intrinsic stretching vibrations of the metal at the tetrahedral site, whereas the U2-lowest band is assigned to octahedral-metal stretching. [20, 21].

**Magnetic properties:**

Fig. (5) Shows the hysteresis loop for all samples. Table (4) lists different parameters such as saturation magnetization ( $M_s$ ), remanent magnetization ( $M_r$ ), the ratio of remanent magnetization to saturation magnetization ( $M_r/M_s$ ) and coercivity.

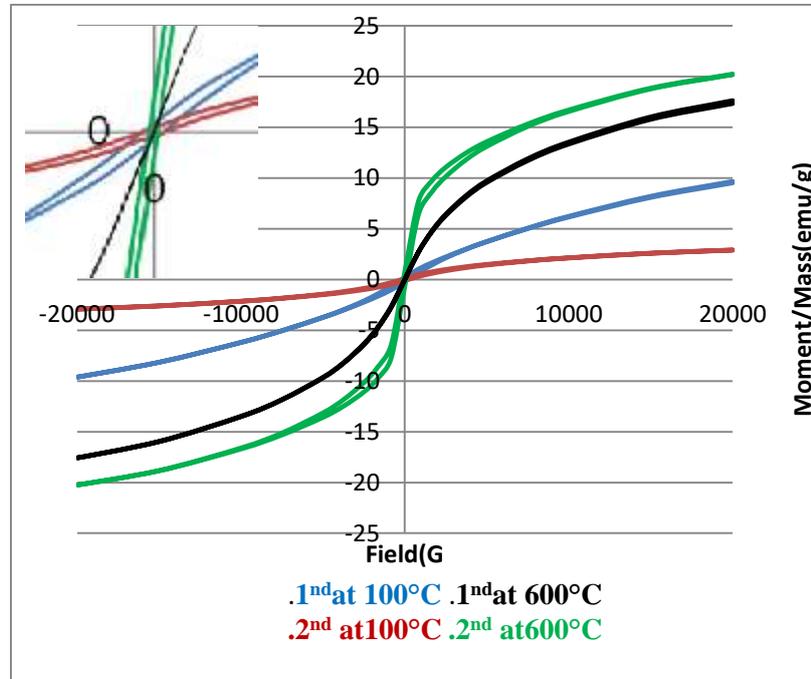

**Fig. (5):** hysteresis loop

**Table (4):** Magnetization data of  $Co_{0.3} Zn_{0.7} Fe_2O_4$

Technique	Temp. (°C)	$M_s$ (emu/g)	$M_r$ (emu/g)	$M_r/M_s$	Coercivity (G)	$\mu_B$ (Bohr magneton)
First	100	9.6503	0.19535	0.02	186.09	0.413
	600	17.592	39.043E-3	0.00	11.992	0.753
Second	100	2.8989	99.179E-3	0.03	206.39	0.124
	600	20.239	0.71282	0.03	83.143	0.867

The saturation magnetization for all samples by two techniques produced at 100 C and 600 C is listed in Table 1 where show that the saturation magnetization in first technique increases from 9.6503:17.592 emu/g but in second technique increases from 2.8989 :20.239 emu/g . This may due to  $Zn^{2+}$  (with zero magnetic moment) replace ion on the tetrahedral A-sites, causing the decrease of magnetic moment in the sublattice  $M_A$ , resulting in the increase of total magnetic moment according to Neel’s equation two sublattice model of ferrimagnetism, the magnetic moment per formula unit in  $\mu_B$ ,  $n_B N(x)$  is expressed as:

$$n_B N(x) = M_B(X) - M_A(X)$$

Where  $M_B$  and  $M_A$  are the B- and A- sublattice magnetic moment in  $\mu_B$  respectively.

Therefore, increase of calcination temperature for samples the saturation magnetization increases. This may be because increase in the lattice parameter, the exchange interaction between A and B sites gets higher resulting in strengthening of A-B interaction and weakening of B-B interaction, which leads to increase of saturation magnetization.

There is positive relationship between grain size and coercivity ( $H_c$ ) in the single domain region according to equation:  $H_c = g - h/D^2$ , where  $g$  and  $h$  are constants and 'D' is the diameter of the particle, this may be because the thermal effects. But the multi domain region there is inverse relationship between grain size and coercivity  $H_c$  according to equation:  $H_c = a + b/D$ , where  $a$  and  $b$  are constants [22, 23, 24]. So, the coercivity reduction with increase in the initial molar concentration (pH suspension) & the calcination temperature with two techniques, which can be attributed to the reduce in anisotropy field for all techniques, which in turn reduces the domain wall energy for first technique less than second technique. These refer to results which the coercivity values reached in first technique from 186.09 to 11.992G and second technique from 206.39 to 83.143G.

## CONCLUSIONS

The conclusions can be drawn from study of  $Co_{0.3}Zn_{0.7}Fe_2O_4$  nanoparticles fabricated by Co-Precipitation method within two techniques as following:

1. The crystallite size depend on the initial molar concentration (pH suspension) & the calcination temperature, where the grain size for first technique in the range of 6.14 : 13 nm but in second technique the range of 8.8: 24.4 nm when the calcination temperature increases from 100 to 600°C respectively.
2. The crystallinity of  $Co_{0.3}Zn_{0.7}Fe_2O_4$  nanoparticles might be improved by increasing calcination temperature but, the crystallinity for second technique better than first technique at 600°C.
3. HRTEM indicates a reliance of particle size and the shape on the initial molar concentration (pH suspension) & the calcination temperatures. The particle size increases in the two techniques, but a nanoparticle has a higher agglomeration degree with the calcination temperature increase in first technique but the reverse occurs in Second technique.
4. Hysteresis loop shows a reduction in corecivity with the initial molar concentration (pH suspension) & the calcination temperature for all techniques to approximate super-paramagnetic behavior.
5. All the coercivity values were low enough to emphasize that the ferrite was a soft ferrite or super-paramagnetic behavior.
6. All laboratory results reveals that the initial molar concentration (pH suspension) & the calcination temperature play a major role to change its structural and magnetic properties significantly.

## Acknowledgement

This work was financial supported by National Water Research Center (NWRC).

## REFERENCES

- [1] K.C.Varma et al, Strl, Microstrl.,Mag . Prop. Of Ni Co Mn Ferrite thin film, J.Of Mag.and Mat., (2011),323,3271-3275.
- [2] Ahmed Saied El-Saaey et al, Effect of Zn Substitution on the characterization of Cobalt Ferrite Nano Particles Prepared Co-precipitation method, IOSR Journal of Applied Chemistry,Volume 7, Issue 11 Ver. II. (Nov. 2014), PP 30-37
- [3] L.J. Zhao, H.J. Zhang, Y. Xing, S.Y. Song, S.Y. Yu, W.D. Shi, X.M. Guo, J.H. Yang, Y.Q. Lei, F. Cao, Journal of Solid State Chemistry,181 (2008) 245.
- [4] N.M. Deraz, J. Anal. Appl. Pyrolysis, 82 (2008) 212
- [5] N. M. Deraz,Moustafa M. G. Fouda,Synthesis, Int. J. Electrochem. Sci 8(2013) 2756.
- [6] S. Ayyappan, J. Philip, B. Raj, Mater. Chem. Phys. 115 (2009) 712
- [7] A. Pradeep, P. Priyadharsini, G. Chandrasekaran, J. Magn. Mater. 320 (2008) 2774.
- [8] X.D. Li, W.S. Yang, F. Li, D.G. Evans, X. Duan, J. Phys. Chem. Solids 67 (2006) 1286
- [9] J.H.Gao, et al. ,Mat. Sci.Eng.B., ,(2004), 110,111.
- [10] P.C.Dorsey,etal, J.Of Appli. Phys. ,(1997), ,81,6884.
- [11] K.H.Buschow, Hnd.bk Of Mag. Mat ,(1995),8,198.
- [12] R.V. Upadhyay, R.V. Metha, K. Parekh, D. Srinivas, R.P. Pant, J. Magn. Mater. 201 (1999) 129.
- [13] Y. Shi, J. Ding, X. Liu, J. Wang, J. Magn. Mater. 205 (1999) 249..
- [14] B. Jeyadevan, C.N. Chinnasamy, K. Shinoda, K.Tothji, J. Appl. Phys. 93 (2003) 8450.
- [15] A.M. El Sayed, Ceram. Int. 28 (2002) 363.
- [16] R. Arulmurugan, B. Jeyadevan, G. Vaidyanathan and S. Sendhilnathan, "Effect of Zinc Substitution on Co-Zn and Mn-Zn Ferrite Nanoferrites Prepared by Co-Precipitation", J. Magn. Mater., 288, 2005, 470-477.
- [17] F. J. Owens and C. P. Poole, The Physics and Chemistry of Nanosolids, New Jersey: John Wiley & Sons, Inc., 2008.
- [18]. V.G. Patil, S.E. Shirsath, S.D. More, S.J. Shukla, K.M. Jadhav, J. Alloys Compd. 488 (2009) 199.
- [19] A. Pradeep and G. Chandrasekaran, "FTIR Study of Ni, Cu and Zn Substituted Nanoparticles of MgFe<sub>2</sub>O<sub>4</sub>," Material Letters, Vol. 60, No. 3, 2006, pp. 371-374.
- [20] Y. Koseoglu, M. Bay, M. Tan, A. Baykal, H. Sozeri, R. Topkaya, N. Akdogan, Magnetic and dielectric properties of Mn<sub>0.2</sub>Ni<sub>0.8</sub>Fe<sub>2</sub>O<sub>4</sub> nanoparticles synthesized by PEG-assisted hydrothermal method, Journal of Nanoparticle Research 13 (2010) 2235–2244.
- [21] R.D.D. Waldron, Infrared Spectra of Ferrite, Physical Review 99 (1955) 1727–17
- [22] B. D. Cullity, "Introduction to Magnetic Materials," AddisonWesely Publishing Company Inc., Reading, Massachusetts,1972.
- [23] S. Chikazumi, "Physics of Magnetism," Wiley, New York, 1959.
- [24] M. George, A. M. John, S. S. Nair, P. A. Joy and M. R. Anantharaman, "Finite Size Effects on the Structural and Magnetic Properties of Sol-Gel Synthesized NiFe<sub>2</sub>O<sub>4</sub>

Powders,” *Journal of Magnetism and Magnetic Materials*, Vol. 302, No. 1, 2006, pp. 190-195.